

# DuPont™ Delrin® 577 BK000

## ACETAL RESIN

### Product Information

Common features of Delrin® acetal resins include mechanical and physical properties such as high mechanical strength and rigidity, excellent fatigue and impact resistance, as well as resistance to moisture, gasoline, lubricants, solvents, and many other neutral chemicals. Delrin® acetal resins also have excellent dimensional stability and good electrical insulating characteristics. They are naturally resilient, self-lubricating, and available in a variety of colors and speciality grades.

Delrin® acetal resin typically is used in demanding applications in the automotive, domestic appliances, sports, industrial engineering, electronics, and consumer goods industries.

**Delrin® 577 is a medium viscosity acetal homopolymer containing 20% glass fiber filler for injection molding. It has very high stiffness, low warpage, and good creep resistance for superior performance at elevated temperature. It contains carbon black for improved weathering.**

General information	Value	Unit	Test Standard
Resin Identification	POM-GF20	-	ISO 1043
Part Marking Code	POM-GF20	-	ISO 11469
Rheological properties	Value	Unit	Test Standard
Melt volume-flow rate	7	cm <sup>3</sup> /10min	ISO 1133
Temperature	190	°C	ISO 1133
Load	2.16	kg	ISO 1133
Molding shrinkage, parallel	1.7	%	ISO 294-4, 2577
Molding shrinkage, normal	1.1	%	ISO 294-4, 2577
Mechanical properties	Value	Unit	Test Standard
Tensile Modulus	4800	MPa	ISO 527-1/-2
Stress at break	52	MPa	ISO 527-1/-2
Strain at break	10	%	ISO 527-1/-2
Flexural Modulus	4600	MPa	ISO 178
Charpy notched impact strength			ISO 179/1eA
73 °F	3	kJ/m <sup>2</sup>	
-22 °F	3	kJ/m <sup>2</sup>	
Thermal properties	Value	Unit	Test Standard
Melting temperature, 18 °F/min	178	°C	ISO 11357-1/-3
Temp. of deflection under load			ISO 75-1/-2
260 psi	118	°C	
65 psi	164	°C	
Coeff. of linear therm. expansion, parallel	56	E-6/K	ISO 11359-1/-2
Coeff. of linear therm. expansion, normal	92	E-6/K	ISO 11359-1/-2
RTI, electrical			UL 746B
60mil	105	°C	
120mil	105	°C	
240mil	105	°C	
RTI, impact			UL 746B
60mil	85	°C	
120mil	85	°C	
240mil	85	°C	
RTI, strength			UL 746B
60mil	90	°C	
120mil	90	°C	
240mil	90	°C	
Flammability	Value	Unit	Test Standard
Burning Behav. at 60mil nom. thickn.	HB	class	IEC 60695-11-10
Thickness tested	1.5	mm	IEC 60695-11-10
UL recognition	yes	-	UL 94
Burning Behav. at thickness h	HB	class	IEC 60695-11-10
Thickness tested	3	mm	IEC 60695-11-10
UL recognition	yes	-	UL 94
FMVSS Class	B	-	ISO 3795 (FMVSS 302)
Burning rate, Thickness 1 mm	<80	mm/min	ISO 3795 (FMVSS 302)

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

Asia Pacific

Tel: +81 3 5521 8600

Europe/Middle East/Africa

Tel: +41 22 717 51 11



# DuPont™ Delrin® 577 BK000

## ACETAL RESIN

Other properties	Value	Unit	Test Standard
Density	1560	kg/m <sup>3</sup>	ISO 1183
Injection	Value	Unit	Test Standard
Drying Recommended	yes		-
Drying Temperature	≥80	°C	-
Drying Time, Dehumidified Dryer	2 - 4	h	-
Processing Moisture Content	≤0.2	%	-
Melt Temperature Optimum	215	°C	-
Min. melt temperature	210	°C	-
Max. melt temperature	20	°C	-
Mold Temperature Optimum	90	°C	-
Min. mold temperature	80	°C	-
Max. mold temperature	100	°C	-
Hold pressure range	80 - 100	MPa	-
Hold pressure time	8	s/mm	-
Annealing time, optional	30	min/mm	-
Annealing temperature	160	°C	-

Characteristics			
Processing	• Injection Molding		
Delivery form	• Pellets		
Additives	• Release agent		
Regional Availability	• North America	• Asia Pacific	• Near East/Africa
	• Europe	• South and Central America	• Global

### Processing Texts

#### Injection molding

Drying is recommended, but not necessary for newly opened packaging stored in a dry location.

Follow the drying guidelines above in the following cases:

- If moisture is above the Processing Moisture Content recommendation,
- When a resin container is damaged,
- When the material is not properly stored in a dry place at room temperature, or
- When packaging stays open for a significant time.

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

#### North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

#### Asia Pacific

Tel: +81 3 5521 8600

#### Europe/Middle East/Africa

Tel: +41 22 717 51 11




# DuPont™ Delrin® 577 BK000


## ACETAL RESIN

### Diagrams

#### Viscosity-shear rate

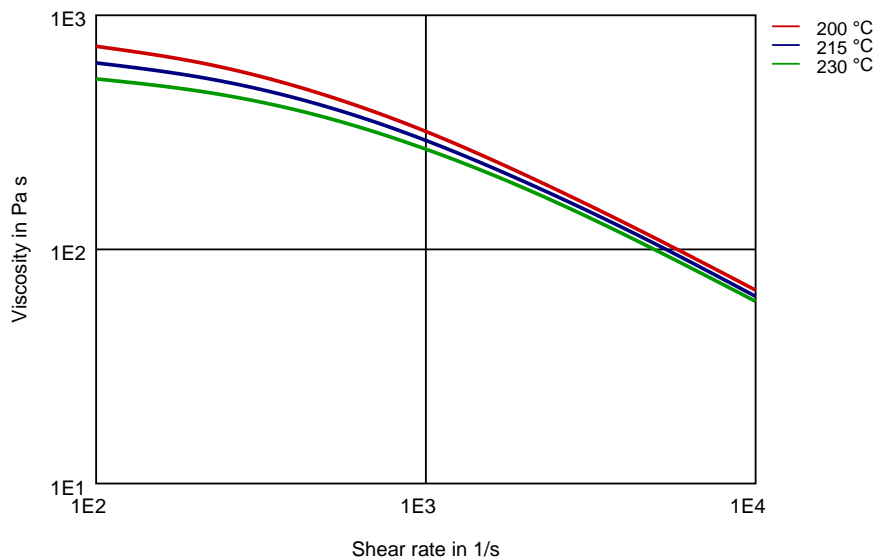

#### Shearstress-shear rate

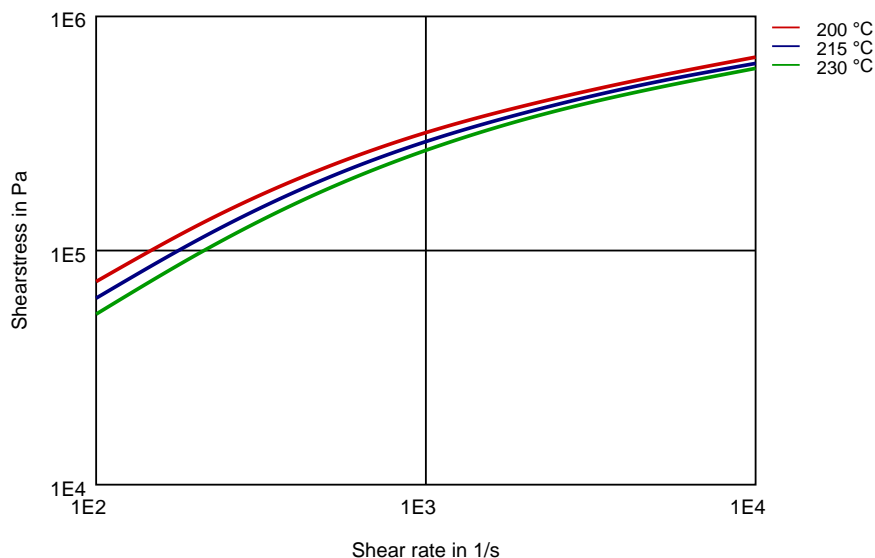

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

#### North America

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

#### Asia Pacific

Tel: +81 3 5521 8600

#### Europe/Middle East/Africa


Tel: +41 22 717 51 11




# DuPont™ Delrin® 577 BK000

## ACETAL RESIN

Dynamic Shear modulus-temperature

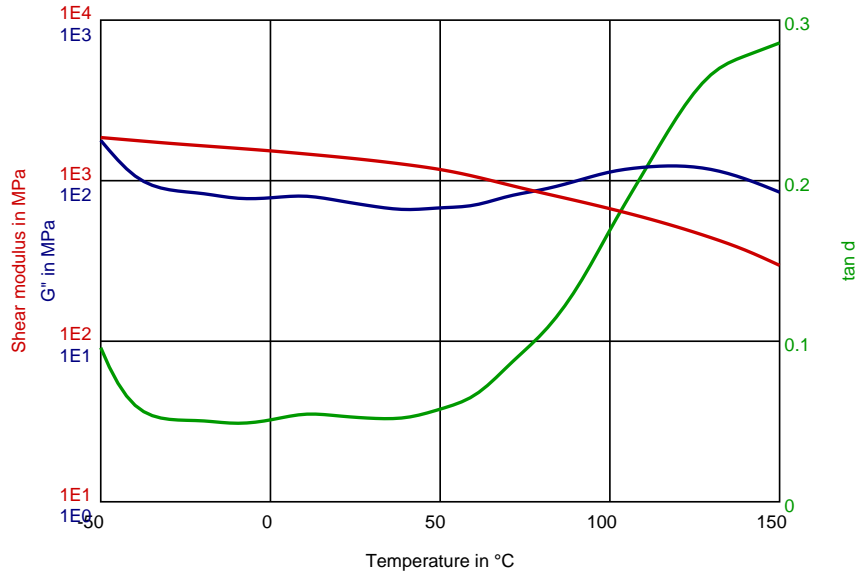

Specific volume-temperature (pvT)

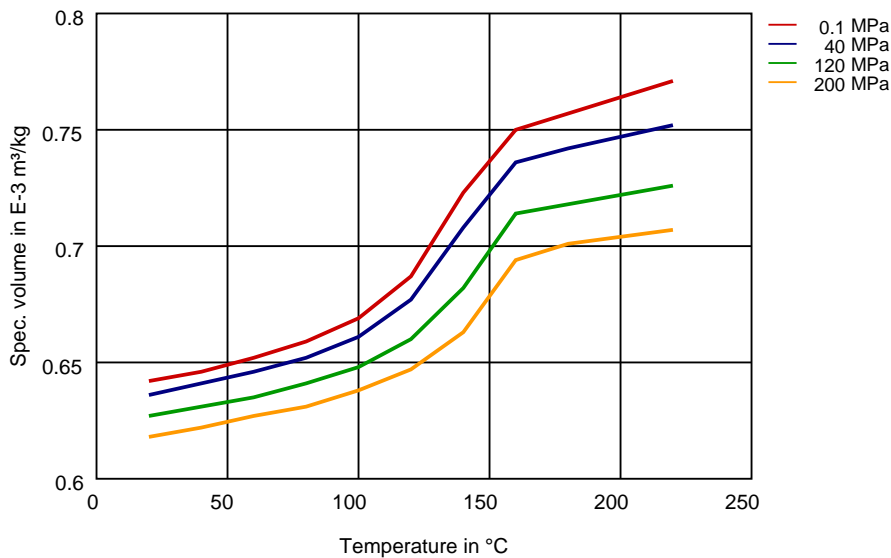

Contact DuPont for Material Safety Data Sheet, general guides and/or additional information about ventilation, handling, purging, drying, etc. ISO Mechanical properties measured at 160 mil (Hytrel® measured at 80 mil), IEC Electrical properties measured at 80 mil, all ASTM properties measured at 120 mil, and test temperatures are 73°F unless otherwise stated.

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

**North America**

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

**Asia Pacific**

Tel: +81 3 5521 8600

**Europe/Middle East/Africa**

Tel: +41 22 717 51 11



# DuPont™ Delrin® 577 BK000

## ACETAL RESIN

The information set forth herein is furnished free of charge and is based on technical data that DuPont believes to be reliable and falls within the normal range of properties. It is intended for use by persons having technical skill, at their own discretion and risk. This data should not be used to establish specification limits nor used alone as the basis of design. Handling precaution information is given with the understanding that those using it will satisfy themselves that their particular conditions of use present no health or safety hazards. Since conditions of product use and disposal are outside our control, we make no warranties, express or implied, and assume no liability in connection with any use of this information. As with any product, evaluation under end-use conditions prior to specification is essential. Nothing herein is to be taken as a license to operate or a recommendation to infringe on patents. Caution: Do not use in medical applications involving permanent implantation in the human body. For other medical applications, discuss with your DuPont customer representative and read Medical Caution H-50103-5.

Copyright © 2017 DuPont or its affiliates. All Rights Reserved. The DuPont Oval Logo, DuPont™, The miracles of science™ and all products denoted with ® or ™ are registered trademarks or trademarks of E.I. du Pont de Nemours and Company or its affiliates.

To find out more, visit [DuPont Performance Polymers](#) or contact nearest DuPont location.

**North America**

Tel: +1 302 999-4592

Toll-Free (USA): 800 441-0575

**Asia Pacific**

Tel: +81 3 5521 8600

**Europe/Middle East/Africa**

Tel: +41 22 717 51 11

